



TEST REPORT



1. NO : CT23-001728E
2. Client
 - Name : SUNGSHIN CEMENT CO.,LTD
 - Address : 18, Maepo-gil, Maepo-eup, Danyang-gun, Chungcheongbuk-do, Republic of Korea
3. Date of Test : 2023.01.04 ~ 2023.03.10
4. Use of Report : Quality Control
5. Test Sample : Ordinary Portland Cement Type I
6. Test Method
 - (1) KS L 5110:2021
 - (2) KS L 5201:2021

Affirmation	Tested By Name : Jong Yoon Son	Technical Manager Name : Shin Kwon Il
This report is not accredited by KOLAS and KS Q ISO/IEC 17025. Our report apply only to the standards or procedures identified and to the sample(s) tested unless otherwise specified. The test results are not indicative of representative of the qualities of the lot from which the sample was taken or of apparently identical or similar products. The results of using only a portion of this report cannot be guaranteed. The authenticity of this test report can be checked on KCL website(www.kcl.re.kr).		

2023.03.10

Korea Conformity Laboratories President Jo, Yung Tae

Result Inquiry : 40, Yeongudangi-ro, Ohchang-Eup, Cheongwon-Gu, Cheongju-si, Chungbuk, Korea (82-43-718-9056)

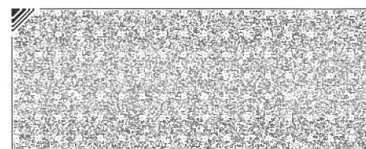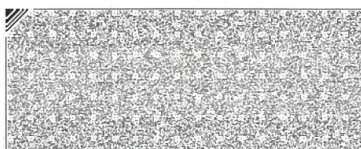

TEST REPORT

No : CT23-001728E

7. Test Results

1) Ordinary Portland Cement Type I

Test Item(s)	Unit	Test Method	Test Results	Remark	Loc.
Specific gravity	Mg/m ³	(1)	3.15	(20±2) °C, (65±10) % R.H.	A
Fineness(blaine)	cm ² /g	(2)	3.810		
Soundness(Lechatelier)	mm	(2)	0.5		
Time of Setting(Initial set)	min	(2)	210		
Time of Setting(Final set)	Hr:min	(2)	4:40		
Compressive strength (3days)	MPa	(2)	32.1		
Compressive strength (7days)	MPa	(2)	41.9		
Compressive strength (28days)	MPa	(2)	54.4	-	
Ignition loss	%	(2)	2.6		
SO ₃	%	(2)	2.7		
MgO	%	(2)	1.6		

※ Location

A : 73, Yangcheong 3-gil, Ochang-eup, Cheongwon-Gu, Cheongju-Si, Chungbuk, Korea

----- End of Report -----

